

Effects of intrabilayer coupling on the magnetic properties of $\text{YBa}_2\text{Cu}_3\text{O}_6$

Anders W. Sandvik

*National High Magnetic Field Laboratory, Florida State University, 1800 E. Paul Dirac Dr.,
Tallahassee, Florida 32306*

Douglas J. Scalapino

Department of Physics, University of California, Santa Barbara, California 93106

(February 1, 2008)

Abstract

A two-layer Heisenberg antiferromagnet is studied as a model of the bilayer cuprate $\text{YBa}_2\text{Cu}_3\text{O}_6$. Quantum Monte Carlo results are presented for the temperature dependence of the spin correlation length, the static structure factor, the magnetic susceptibility, and the ^{63}Cu NMR spin-echo decay rate $1/T_{2G}$. As expected, when the ratio J_2/J_1 of the intrabilayer and in-plane coupling strengths is small, increasing J_2 pushes the system deeper inside the renormalized classical regime. Even for J_2/J_1 as small as 0.1 the correlations are considerably enhanced at temperatures as high as $T/J_1 \approx 0.4 - 0.5$. This has a significant effect on $1/T_{2G}$, and it is suggested that measurements of this quantity at high temperatures can reveal the strength of the intrabilayer coupling in $\text{YBa}_2\text{Cu}_3\text{O}_6$.

One of the unresolved issues regarding the high- T_c cuprate superconductors is the role of the coupling between CuO_2 planes within the same “block” in bi- and tri-layer compounds. Suggestions^{1,2} that this coupling might be responsible for the spin-gap behavior observed³ in the bilayer cuprate $\text{YBa}_2\text{Cu}_3\text{O}_{6.6}$ has spurred recent theoretical work on models of two coupled CuO_2 planes.^{4–6} Experimentally, the strength of the intrabilayer coupling in $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ has not yet been accurately determined. Neutron scattering experiments performed in the insulating regime have not detected the high-energy branch of the spin-fluctuation spectrum up to energies of 60meV.⁷ This negative result analyzed in the framework of a linear spin-wave theory suggests a lower bound of $J_2 = 8 \text{ meV}$.⁷ In the recently synthesized high- T_c superconductor $\text{YBa}_4\text{Cu}_7\text{O}_{15}$ the two planes constituting a bilayer have slightly different chemical environments,⁸ enabling various cross-relaxation experiments.⁹ Analyzing such experiments by Stern *et al.*,¹⁰ Millis and Monien estimated $5 \text{ meV} < J_2 < 20 \text{ meV}$.⁶ On the other hand, quantum chemical calculations indicate a value of J_2 in $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ as high as $\approx 50 \text{ meV}$.¹¹ In this situation, it is important to consider new possible experiments that could accurately determine the magnitude of J_2 .

Here we explore possibilities of extracting the strength of the intrabilayer coupling from experiments in the antiferromagnetic insulating regime, e.g. for $\text{YBa}_2\text{Cu}_3\text{O}_6$. We report results of quantum Monte Carlo (QMC) simulations of a two-layer Heisenberg model defined by the hamiltonian

$$\hat{H} = J_1 \sum_{a=1,2} \sum_{\langle i,j \rangle} \vec{S}_{ai} \cdot \vec{S}_{aj} + J_2 \sum_i \vec{S}_{1i} \cdot \vec{S}_{2i}, \quad (1)$$

where $\vec{S}_{ai}$ is a spin-1/2 operator at site i of layer a , and $\langle i,j \rangle$ denotes a pair of nearest-neighbor sites on a square lattice. This model should be a reasonable starting point for describing the magnetic properties of $\text{YBa}_2\text{Cu}_3\text{O}_6$ at temperatures higher than the Neel temperature, which in clean samples is as high as 500K. Since the in-plane coupling $J_1 \approx 1200K$,⁷ temperatures of interest are $0.4 \lesssim T/J_1 \lesssim 0.5$. We present results in this regime for the spin-spin correlation length, the static structure factor, the susceptibility, and the ^{63}Cu NMR spin-echo decay rate $1/T_{2G}$, and discuss the possibilities to experimentally detect the

influence of a weak J_2 .

The finite-temperature physics of two-dimensional quantum antiferromagnets was explained in the framework of a mapping onto a nonlinear σ -model some time ago by Chakravarty, Halperin and Nelson.¹² If the ground state is ordered the correlation length ξ in the low-temperature renormalized classical (RC) regime diverges as $e^{2\pi\rho_s/T}$, where ρ_s is the spin-stiffness constant. At temperatures $T \gg \rho_s$, T is the only relevant energy scale and the behavior is quantum critical (QC), with $\xi \sim T^{-1}$.^{12,13} If ρ_s is large, the cross over boundary between the RC and QC regimes of the σ -model may be at a temperature where a σ -model description of the antiferromagnet is no longer valid, and instead there is a direct cross-over from the RC to a local moment (LM) regime where the spins are essentially decoupled.

For a single Heisenberg plane ($J_2/J_1 = 0$), the behavior at the temperatures of interest here is influenced by all the above regimes. For $0.4 \lesssim T/J_1 \lesssim 0.6$ there is a cross-over from RC to QC behavior, and at higher temperatures LM effects influence the behavior in the narrow QC regime.^{14,15} For the two-layer model described by (1), the ground state order increases with J_2 for small J_2/J_1 , and has a maximum around $J_2/J_1 \approx 0.8$ before decreasing due to the tendency to singlet formation across the planes for larger J_2 .^{2,16} A quantum phase transition to a disordered ground state occurs at $(J_2/J_1)_c \approx 2.5$.^{17,18} The finite-temperature properties of near-critical systems have been studied numerically in detail, enabling a direct verification of the applicability of $1/N$ calculations for the nonlinear σ -model in the QC regime.^{18,14,19} Here we are concerned with values of J_2/J_1 more reasonable for modeling high- T_c bilayer cuprates, and choose $J_2/J_1 = 0.1, 0.2$, and 0.5 . Owing to the enhanced ground state order for this range of J_2/J_1 , one can expect the system to exhibit RC behavior at temperatures higher than for a single layer.² Below we present quantitative results for several experimentally accessible quantities.

We begin by defining spin operators that are symmetric and antisymmetric with respect to interchange of the two layers:

$$\vec{S}_{\pm}(i) = \vec{S}_{1i} \pm \vec{S}_{2i}. \quad (2)$$

Using these we have calculated the correlation functions

$$C_{\pm}(\vec{r}_i - \vec{r}_j) = \langle S_{\pm}^z(i) S_{\pm}^z(j) \rangle, \quad (3)$$

the corresponding static structure factors

$$S_{\pm}(\vec{q}) = \frac{1}{2L^2} \sum_{i,j} e^{i\vec{q} \cdot (\vec{r}_i - \vec{r}_j)} C_{\pm}(\vec{r}_i - \vec{r}_j), \quad (4)$$

and static susceptibilities

$$\chi_{\pm}(\vec{q}) = \frac{1}{2L^2} \sum_{i,j} e^{i\vec{q} \cdot (\vec{r}_i - \vec{r}_j)} \int_0^{\beta} d\tau \langle S_{\pm}^z(i, \tau) S_{\pm}^z(j, 0) \rangle, \quad (5)$$

where $S_{\pm}^z(i, \tau) = e^{\tau \hat{H}} S_{\pm}^z(i) e^{-\tau \hat{H}}$, and L is the linear size of the system. The normalization in (4) and (5) has been chosen such that the standard definitions for a single plane are recovered for $J_2/J_1 = 0$. For the numerical simulations we have used a QMC method based on stochastic series expansion²⁰ (a generalization of Handscomb's method²¹), which is free from errors of the ‘‘Trotter approximation’’ used in standard methods.²² All results presented here are for $2 \times 64 \times 64$ lattices ($L = 64$).

In order to extract the correlation length we fit the correlation function $C_{-}(r)$ to the nonlinear σ -model forms discussed in Ref. 19. The results are shown in Fig. 1. For $J_2/J_1 = 0$ we find good agreement with the results by Makivić and Ding.²³ The enhancement of the correlations with increasing J_2/J_1 is evident. The correlation length quickly approaches the size of the lattice as T is lowered below $T/J_1 \approx 0.4 - 0.5$, and in order to obtain reliable results for ξ at lower temperatures lattices larger than $L = 64$ would have to be used.

The correlation lengths graphed in Fig. 1 exhibit the exponential growth characteristic of the RC regime, as expected.² In order to more quantitatively address the question at what temperature the RC description is valid for a given J_2/J_1 we study the ratio $S_{-}(\pi, \pi)/[T\chi_{-}(\pi, \pi)]$. In a classical system one always has $S/(\chi T) = 1$ (for any $\vec{q}$). A characteristic of the quantum antiferromagnet in the RC regime is that this relation remains satisfied close to the antiferromagnetic wave-vector.¹² On the other hand, for a single plane in the QC regime $S(\pi, \pi)/[T\chi(\pi, \pi)] \approx 1.1$.^{13,24,19} For a two-layer model in the QC regime,

the gapped mode cannot be neglected if the temperature is of the same order as the gap, $\Delta \propto \sqrt{J_1 J_2}$, and $S(\pi, \pi)/[T\chi(\pi, \pi)]$ will probably differ slightly from the above one-layer σ -model prediction. In any case, the RC value for this quantity should be 1, and is hence useful for determining whether the system is in the RC regime or not. The results displayed in Fig. 2 clearly indicate that the coupled planes approach the RC regime considerably faster than a single plane.

The frequency integrated neutron scattering intensity is given by a combination of the structure factors $S_+(\vec{q})$ and $S_-(\vec{q})$, with weights depending on the momentum transfer perpendicular to the planes.⁷ Since the fluctuations corresponding to $S_+(\vec{q})$ are gapped at $\vec{q} = (\pi, \pi)$, $S_+(\pi, \pi)$ saturates below a temperature set by the gap, whereas $S_-(\pi, \pi)$ diverges. Fig. 3 shows $J_2/J_1 = 0.1$ results for $\vec{q}$ close to (π, π) . The ratio $S_-(\pi, \pi)/S_+(\pi, \pi)$ is ≈ 4 already at $T/J_1 = 0.5$, and increases rapidly with decreasing T . At $T/J_1 = 0.4$ the ratio is almost 30 (not shown in the figure). The smallness of $S_+(\vec{q})$ for $\vec{q}$ close to (π, π) may make the detection of the high-energy mode difficult, in particular because the even and odd modes cannot be completely separated experimentally.⁷

In Fig. 4 shows results for the uniform susceptibility per spin, $\chi = \chi_+(q = 0)$. The susceptibility for $J_2/J_1 \leq 0.2$ is very close to the single-plane result over the whole temperature range considered here. The linear behavior seen for the single plane in the temperature regime $0.35 \lesssim T/J \lesssim 0.55$ is in close quantitative agreement with the prediction for the QC regime,¹³ despite of the fact that the system actually crosses over to the RC regime at these temperatures (see Fig. 2).^{14,15} An approximately linear behavior persists at these temperatures also for the systems with $J_2/J_1 = 0.2$ and 0.5 , which are even deeper inside the RC regime. It would be interesting to compare the behavior with the QC and RC predictions for these couplings. As discussed above, this probably requires calculations for a full two-layer non-linear σ -model.

We now turn to what we consider the most promising experiment for determining J_2 in the insulating regime. Recently, we showed¹⁵ that the NMR rates $1/T_1$ and $1/T_{2G}$ for La_2CuO_4 measured by Imai *et al.*²⁸ and Matsumura *et al.*²⁹ are well reproduced within the

single-layer Heisenberg model and known hyperfine form factors (for the high-temperature regime, similar results were obtained by Sokol and co-workers^{24,30}). At high temperatures both $1/T_1$ and $1/T_{2G}$ show evidence of QC behavior, although the proximity to the RC and LM regimes influences the behavior as well. As shown above, even a small intrabilayer coupling pushes the system considerably further inside the RC regime. As a consequence, a system with $J_2/J_1 \approx 0.1 - 0.2$ should exhibit no QC behavior in the experimentally accessible temperature range. Below we present QMC results for $1/T_{2G}$ which should be useful for direct comparisons with experiments.

The gaussian component of the spin-echo decay rate is related to the the nuclear spin-spin interactions mediated by the electronic spins. The coupling of a ^{63}Cu nuclear spin $\vec{I}_0$ at site 0 in plane a to surrounding electronic spins is approximately given by the Mila-Rice form^{25,26}

$$^{63}\hat{H} = A_{\perp}(I_0^x S_{a0}^x + I_0^y S_{a0}^y) + A_{\parallel} I_0^z S_{a0}^z + B \sum_{\delta} \vec{I}_0 \cdot \vec{S}_{a\delta}, \quad (6)$$

where δ denotes a nearest-neighbor of site 0. The hyperfine coupling constants $A_{\perp}$, $A_{\parallel}$ and B are known from Knight shift measurements.²⁶ Pennington and Slichter derived the following form for $1/T_{2G}$, expected to be valid for the cuprates²⁷:

$$\frac{1}{T_{2G}} = \left[\frac{0.69}{2\hbar^2} \sum_{\vec{x} \neq 0} J_z^2(0, \vec{x}) \right]^{1/2}. \quad (7)$$

Here $J_z(\vec{x}_1, \vec{x}_2)$ is the z -component of the induced interaction between nuclei at $\vec{x}_1$ and $\vec{x}_2$,

$$J_z(\vec{x}_1, \vec{x}_2) = -\frac{1}{2} \sum_{i,j} A(\vec{x}_1 - \vec{r}_i) A(\vec{x}_2 - \vec{r}_j) \chi(i - j), \quad (8)$$

where for the hyperfine coupling (6) one has $A(0) = A_{\parallel}$, $A(1) = B$, and $A(r) = 0$ otherwise. $\chi(i - j)$ is the static susceptibility (5) written in coordinate space. Note that $\vec{x}$ in Eq. (7) runs over all the spins of both planes, except the spin at site 0 in the plane where the nucleus considered resides. The constant 0.69 in (7) is the natural abundance of the ^{63}Cu isotope.

In Fig. 5 we present results for J_1/T_{2G} versus T/J_1 in units of K/s. The results expected in an experiment can be obtained by dividing with the relevant value of J_1 . We have

used the standard experimental values for the hyperfine couplings; $B = 41\text{kOe}/\mu_B$ and $A_{\parallel} = -4B$.²⁶ In Ref. 18 we have shown that the QMC results for $J_2 = 0$ agree well with the measurements on La_2CuO_4 ^{28,29} (the best agreement is obtained with a slightly smaller value for B ; $B \approx 37\text{kOe}/\mu_B$). We believe that our $1/T_{2G}$ QMC results in Fig. 5 will be useful for determining the value of J_2 in $\text{YBa}_2\text{Cu}_3\text{O}_6$, provided that measurements can be carried out in the regime of temperatures $500\text{K} \lesssim T \lesssim 800\text{K}$. A potential difficulty is that J_1 has to be known to rather high accuracy in order to establish the relation to the temperature scale of Fig. 5.

In summary, we have studied the effects of a small intrabilayer coupling on the properties of the two-dimensional Heisenberg model. Even coupling ratios J_2/J_1 as small as 0.1-0.2 push the boundary of the RC regime up close to the highest temperatures accessible experimentally. This should have detectable consequences for a number of quantities. In particular, we suggest that measurements of the spin-echo decay rate $1/T_{2G}$ at high temperatures would be useful for determining the strength of the intrabilayer coupling in $\text{YBa}_2\text{Cu}_3\text{O}_6$. The spin-lattice relaxation rate, which we have not yet calculated for the two-layer model, should also be a sensitive probe.

We would like to thank A. Chubukov, A. Millis, and H. Monien for useful discussions. Most of the computations were carried out on a cluster of DEC Alpha 3000/400 workstations at the Supercomputer Computations Research Institute at Florida State University. This work was financially supported by the Office of Naval Research under Grant No. ONR N00014-93-0495, and the Department of Energy under Grant No. DE-FG03-85ER45197. A.W.S. would like to thank the Department of Physics at UC Santa Barbara for its hospitality while part of this work was carried out.

REFERENCES

- ¹ B. Altshuler and L. Ioffe, Solid State Commun. **82**, 253 (1992).
- ² A. J. Millis and H. Monien, Phys. Rev. Lett. **70**, 2813 (1992); Phys. Rev. B **50**, 16606 (1994).
- ³ M. Takigawa *et al.*, Phys. Rev. B **42**, 243 (1991).
- ⁴ B. L. Altshuler *et al.*, JETP Lett. **59**, 65 (1994).
- ⁵ M. Ubbens and P. A. Lee, Phys. Rev. B **50**, 438 (1994).
- ⁶ A. J. Millis and H. Monien, unpublished.
- ⁷ S. Shamoto *et al.*, Phys. Rev. B **48**, 13817 (1993).
- ⁸ R. Stern *et al.* Phys. Rev. B **50**, 426 (1994).
- ⁹ H. Monien and T. M. Rice, Physica C **235-240**, 1705 (1994).
- ¹⁰ R. Stern, M. Mali, J. Roos, and D. Brinkmann, Phys. Rev. B **51**, 15478 (1995).
- ¹¹ F. Barriquand and G. A. Sawatzky, Phys. Rev. B **50**, 16649 (1994).
- ¹² S. Chakravarty, B. I. Halperin, and D. R. Nelson, Phys. Rev. Lett. **60** 1057 (1988); Phys. Rev. B **39**, 2344 (1989).
- ¹³ S. Sachdev and J. Ye, Phys. Rev. Lett. **69** (1992) 2411; A. V. Chubukov and S. Sachdev, Phys. Rev. Lett. **71** 169 (1993).
- ¹⁴ N. Elstner *et al.*, Phys. Rev. B **51** 8984 (1995).
- ¹⁵ A. W. Sandvik and D. J. Scalapino, Phys. Rev. B **51** 9403 (1995).
- ¹⁶ A. V. Chubukov and D. Morr, Phys. Rev. B **52**, 3521 (1995).
- ¹⁷ K. Hida, J. Phys. Soc. Jpn., **61**, 1013 (1992).
- ¹⁸ A. W. Sandvik and D. J. Scalapino, Phys. Rev. Lett. **72**, 2777 (1994).

- ¹⁹ A. W. Sandvik, A. V. Chubukov, and S. Sachdev, Phys. Rev. B **51**, 16483 (1995).
- ²⁰ A. W. Sandvik and J. Kurkijärvi, Phys. Rev. B **43**, 5950 (1991); A. W. Sandvik, J. Phys. A **25**, 3667 (1992).
- ²¹ D. C. Handscomb, Proc. Cambridge Philos. Soc. **58**, 594 (1962); **60**, 116 (1964).
- ²² J. E. Hirsch *et al.*, Phys. Rev. B **26**, 5033 (1982).
- ²³ M. S. Makivić and H.-Q. Ding, Phys. Rev. B **43**, 3562 (1991).
- ²⁴ A. Sokol, R. L. Glenister, and R. R. P. Singh, Phys. Rev. Lett., **72**, 1549 (1994).
- ²⁵ F. Mila and T. M. Rice, Physica C **157**, 561 (1989).
- ²⁶ A. J. Millis, H. Monien, and D. Pines, Phys. Rev. B **42**, 167 (1990).
- ²⁷ C. H. Pennington and C. P. Slichter, Phys. Rev. Lett. **66**, 381 (1991).
- ²⁸ T. Imai *et al.*, Phys. Rev. Lett. **70**, 1002 (1993); **71**, 1254 (1993).
- ²⁹ M. Matsumura *et al.*, J. Phys. Soc. Jpn. **63**, 4331 (1994).
- ³⁰ A. Sokol, E. Gagliano, and S. Bacci, Phys. Rev. B **47**, 14646 (1993).

FIGURES

FIG. 1. The spin-spin correlation length vs. temperature for various strengths of the intrabilayer coupling.

FIG. 2. The ratio $S_-(\pi, \pi)/[T\chi_-(\pi, \pi)]$ vs. T for various intrabilayer couplings. In the RC regime this ratio is 1. The dashed line is the nonlinear σ -model result for a single plane.

FIG. 3. The odd (upper panel) and even (lower panel) static structure factors for $J_2/J_1 = 0.1$ close to the antiferromagnetic wave-vector $\vec{q} = (\pi, \pi)$ at temperatures close to $T/J_1 = 0.5$.

FIG. 4. The temperature dependence of the uniform susceptibility per spin for various intrabilayer coupling strengths.

Fig. 5. The ^{63}Cu spin-echo decay rate $1/T_{2G}$ multiplied by the in-plane coupling J_1 vs. T/J_1 for various values of the intrabilayer coupling strength.

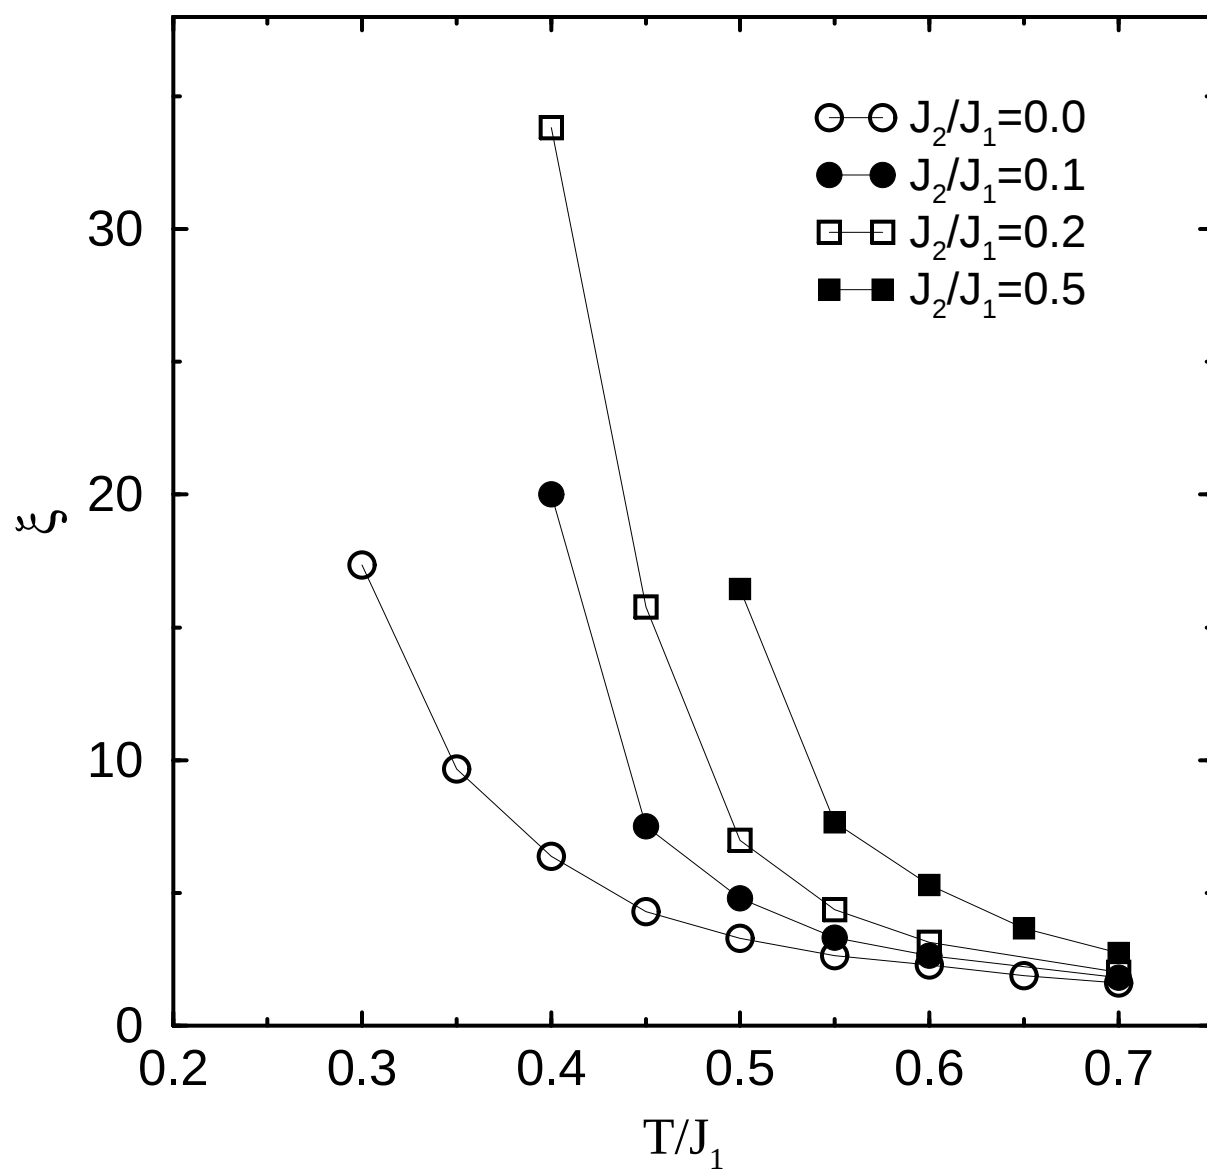


FIG. 1

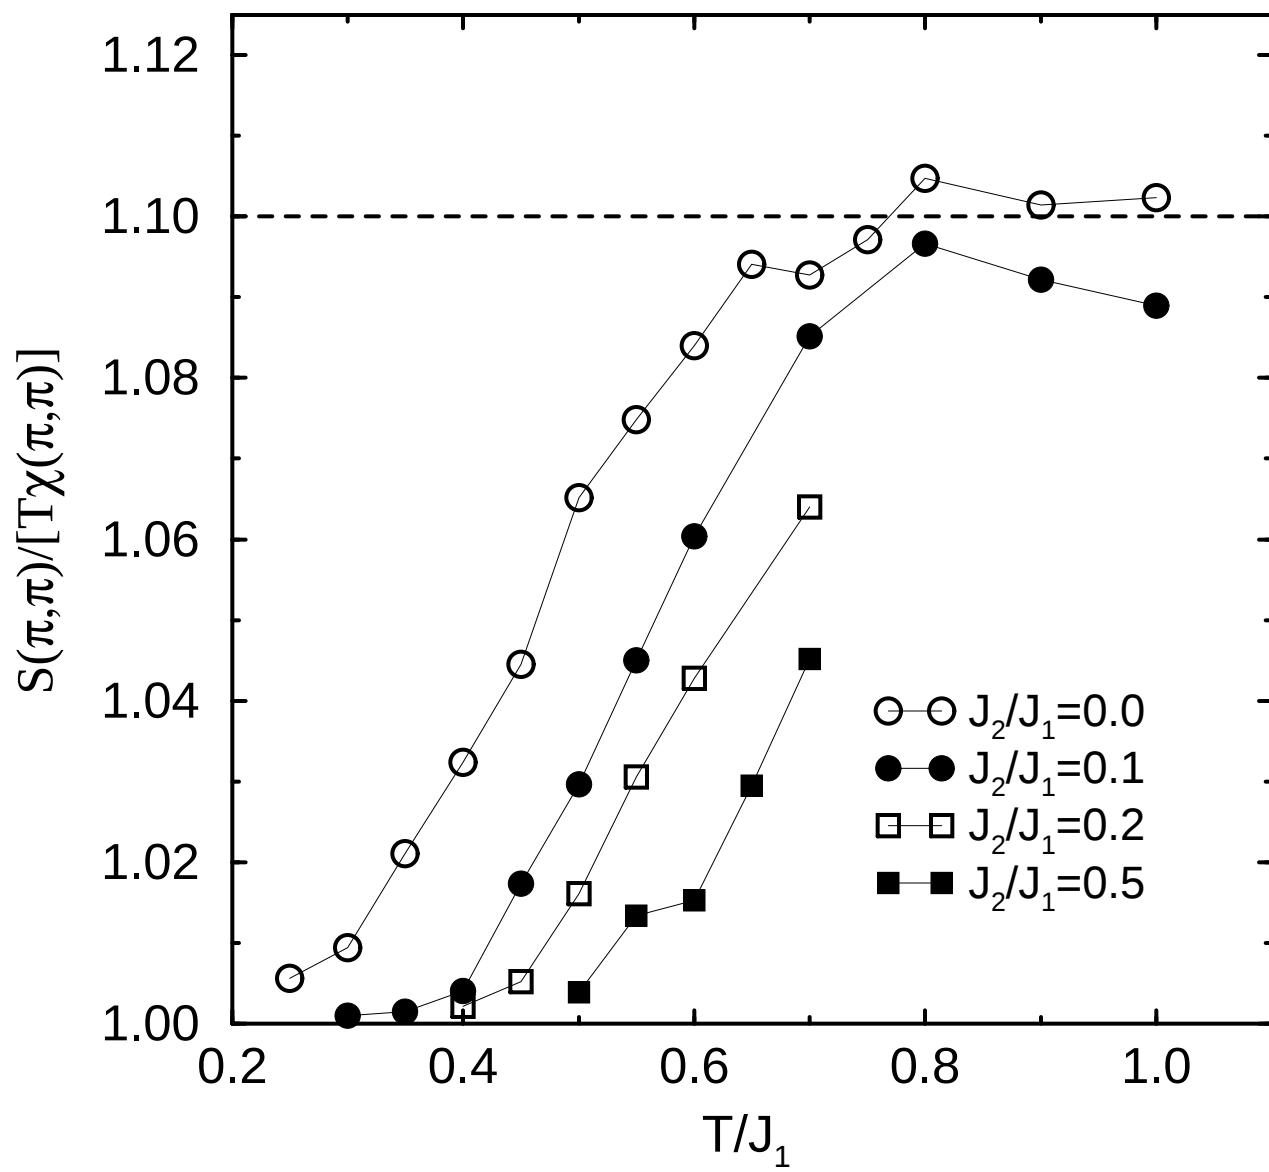


FIG. 2

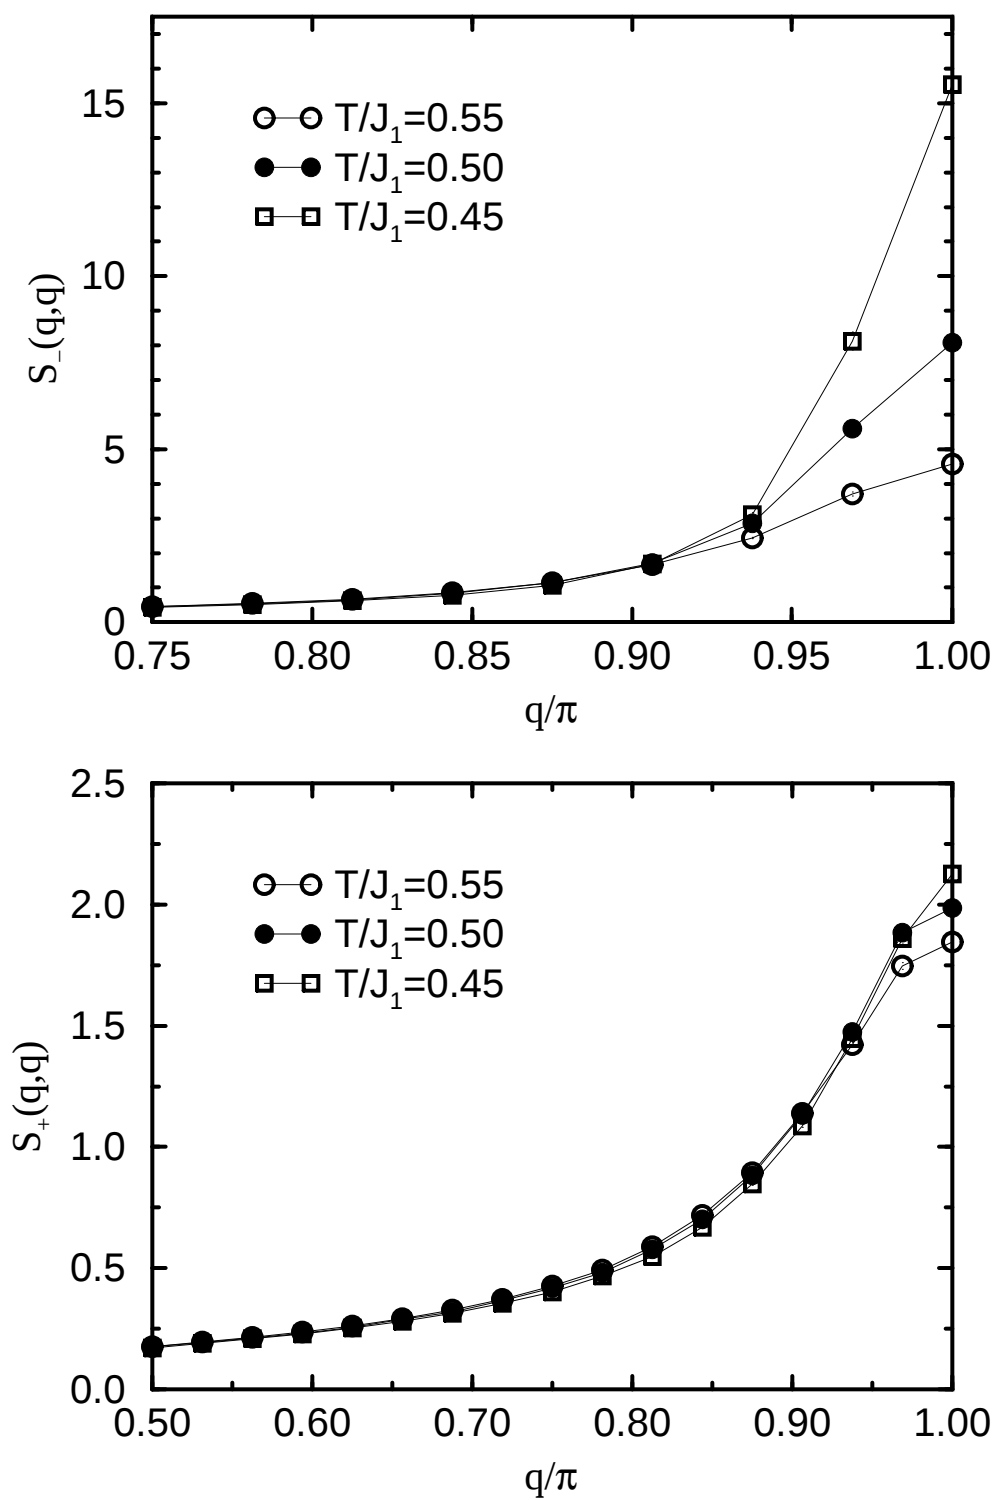


FIG. 3

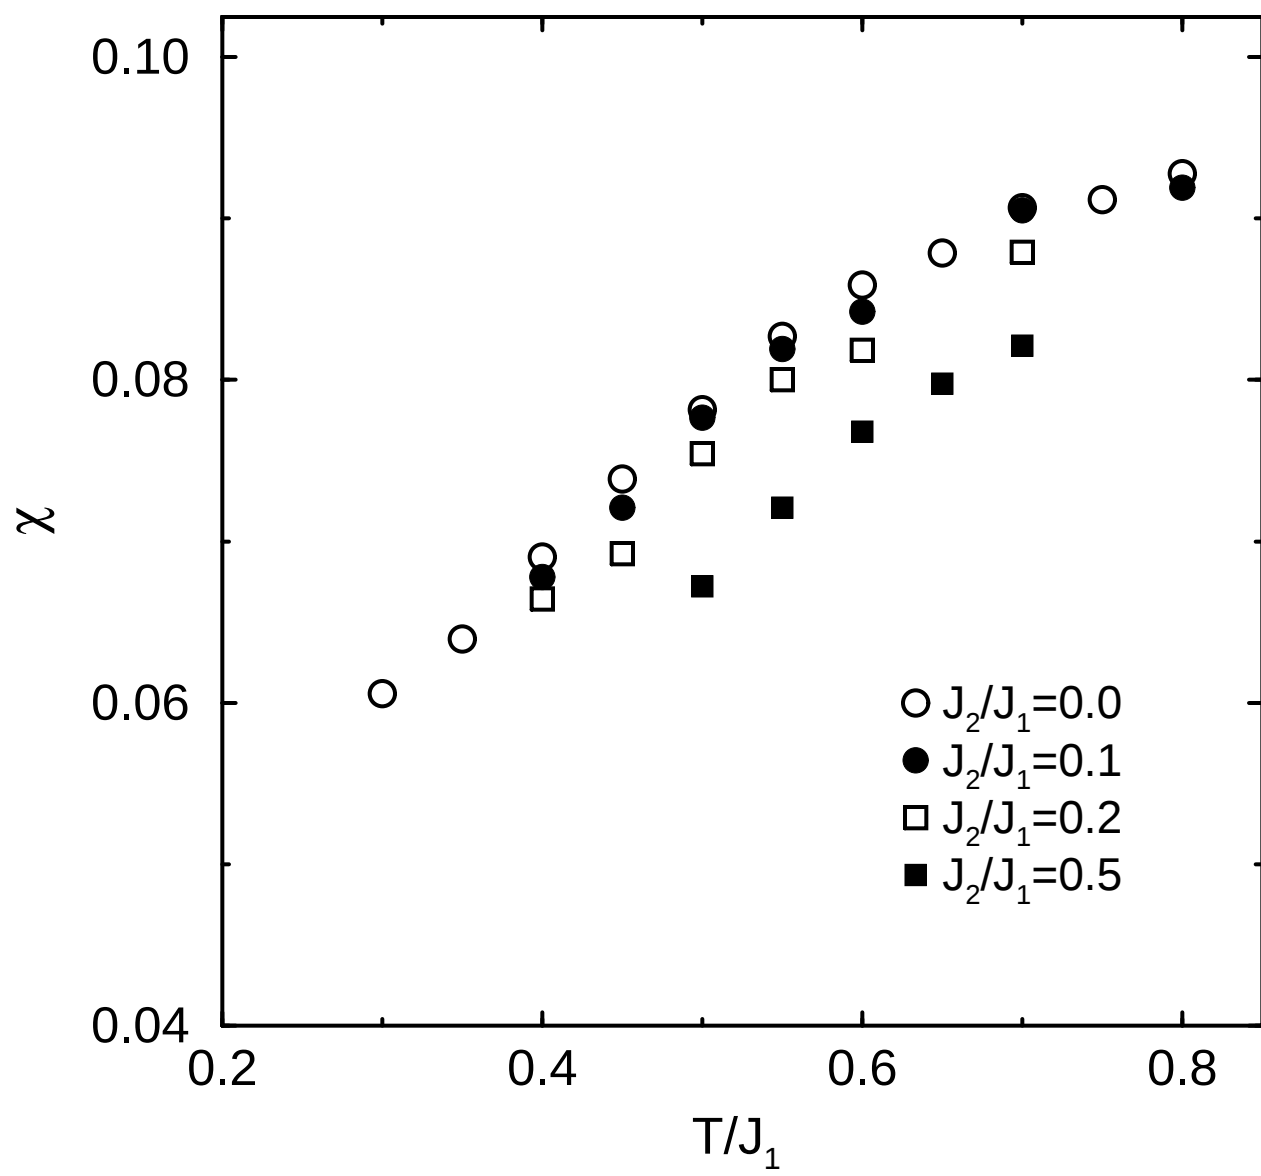


FIG. 4

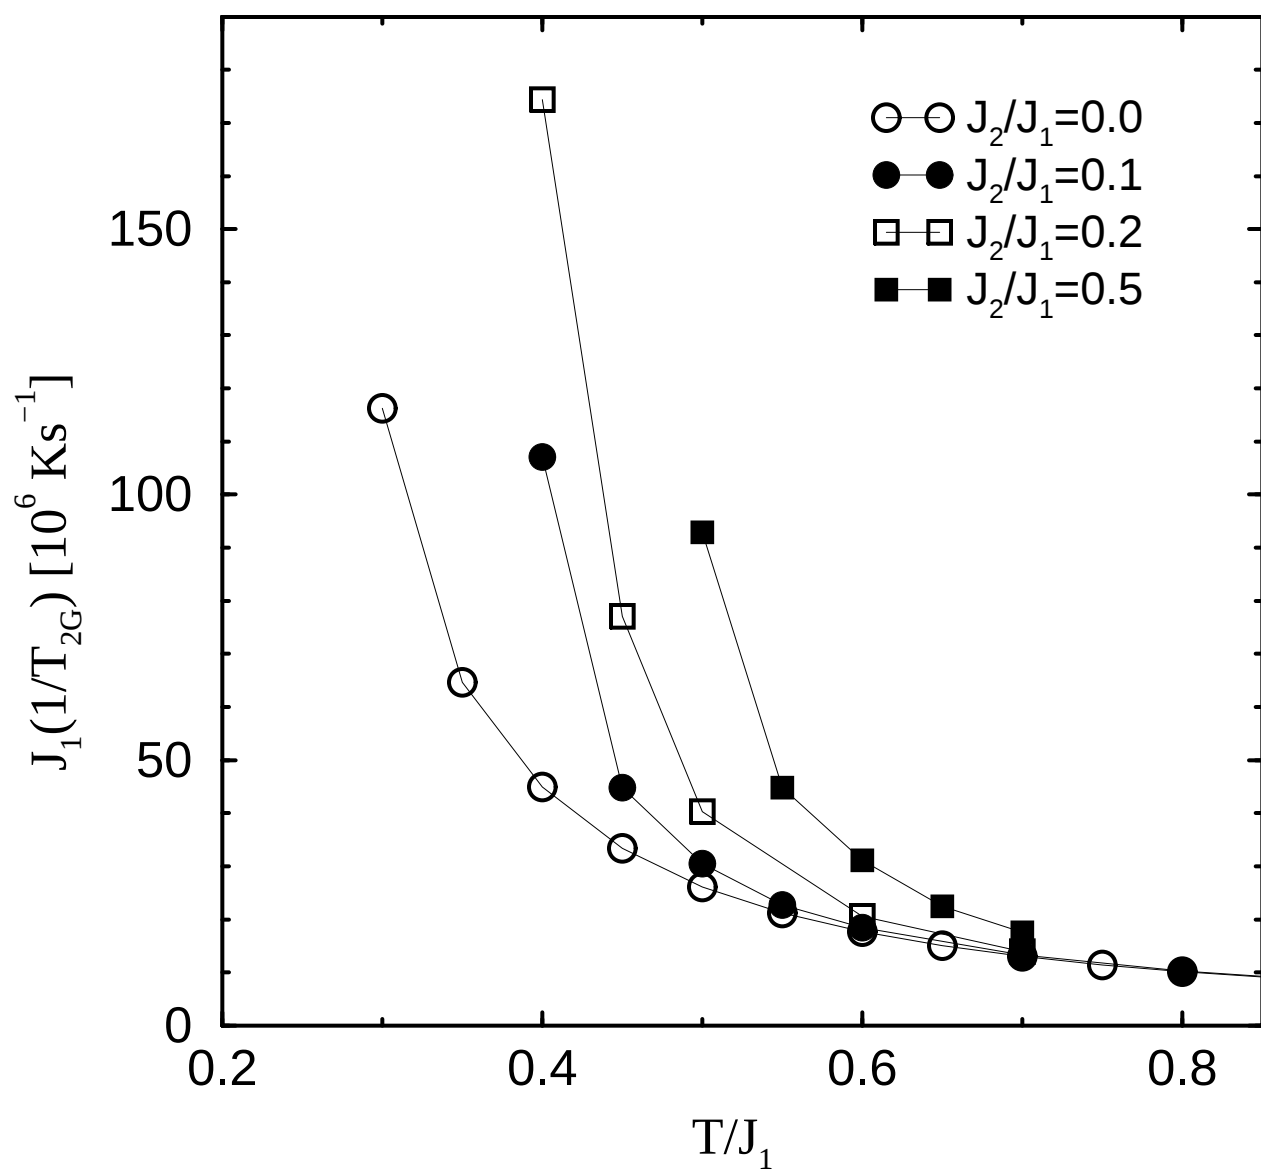


FIG. 5